

Synthesis of Well-Defined Macroporous Polymer Monoliths by Sol–Gel Polymerization in Supercritical CO₂

Andrew I. Cooper,* Andrew B. Holmes[†]

[†] Melville Laboratory for Polymer Synthesis, University of Cambridge, Pembroke St.,
Cambridge, CB2 3RA, UK

E-mail: abh1@cus.cam.ac.uk, Fax: +44 (0)1223 334866

* Department of Chemistry, University of Liverpool, Crown St., Liverpool, L69 7ZD, UK

E-mail: aicooper@liv.ac.uk, Fax: +44 (0)151 7943588

<http://www.andrewcooper.com>

The synthesis of continuous macroporous polymers (*i.e.*, ‘polymer monoliths’) is currently a subject of great interest for a wide range of applications. These materials have certain advantages over more traditional macroporous polymer beads, mainly because of the absence of interstitial voids in the ‘packed’ state. Typically, a mould is filled with a polymerization mixture containing a cross-linking monomer, functional comonomers, initiator, and a porogenic diluent. This mixture is then polymerized to form a continuous porous monolith which conforms to the shape of the mould. One drawback of the method is that large volumes of organic solvents are required (typically ~ 1:1 solvent to monomer) and these solvents may be hard to remove from the polymer matrix at the end of the reaction. Also, the pore structure of the polymer can be remarkably sensitive to very small changes in the composition of the porogenic solvent mixture. Recently, we have developed methods for the synthesis of highly cross-linked polymer monoliths using supercritical carbon dioxide as the porogenic solvent (A.I. Cooper and A.B. Holmes, *Adv. Mater.*, **1999**, *11*, 2170). In this paper we describe how it is possible to achieve fine control over average pore sizes and pore size distributions, both by varying the density of the supercritical solvent and also *via* reverse micellar imprinting.

Introduction.

Macroporous cross-linked polymers are extremely useful in a wide range of applications.¹ Unlike lightly cross-linked polymers which become porous when swollen by solvents, macroporous polymers have a permanent porous structure which is formed during their preparation and persists in the dry state. The internal macroporous morphology is characterized by interconnected channels (pores) which permeate the rigid, extensively cross-linked polymer matrix. Macroporous resins are often synthesized in the form of uniform beads by suspension polymerization;^{2,3} however, this can lead to performance limitations in certain applications, notably the chromatographic separation of large molecules. A very promising alternative approach has been the synthesis of continuous, macroporous monolithic polymers,^{4,5} which have been developed for a variety of applications including HPLC, solid phase extraction, high-performance membrane chromatography (HPMC), capillary electrochromatography, molecular imprinting, and high-throughput bioreactors. Most systems so far have involved the free radical polymerization of methacrylate or styrene based cross-linkers (*e.g.*, ethyleneglycol dimethacrylate, divinyl benzene). The porogenic diluent may be

either solvating or non-solvating in nature, and carefully chosen ternary solvent mixtures can be used to allow fine control of the porous properties of the monolithic polymers. In some cases, materials have been optimized to incorporate a distribution of small, diffusive pores (< 100 nm), interconnected with larger, flow-through pores with diameters in the range 700–2000 nm. A key advantage of this methodology is that the macroporous polymers can be prepared directly within a variety of different containment vessels, including both wide bore chromatography columns and narrow bore capillaries.

Carbon dioxide is an attractive solvent for polymer chemistry because it is inexpensive, non-toxic, and non-flammable.^{6,7} DeSimone and others have shown that supercritical CO₂ (scCO₂) is a versatile medium for both homogeneous and heterogeneous polymerization.^{8–11} Supercritical carbon dioxide has also been used for the formation of microcellular polymer foams^{12–14} and aerogels.¹⁵ Previously, we demonstrated the synthesis of highly cross-linked polymers by heterogeneous polymerization in scCO₂.¹⁶ Dry, free-flowing powders were generated, either as irregular microparticles or, with the addition of CO₂-soluble surfactants, as uniform polymer microspheres (0.4–10 μm).¹⁷ In all cases, the polymers were shown to be completely non-porous. More recently, we described for the first time the synthesis of highly cross-linked macroporous polymer monoliths using scCO₂ as the porogenic solvent.¹⁸ This approach eliminates the need for any organic solvent in the polymerization procedure and allows the formation of truly solvent-free products. Herein we discuss how the average pore sizes and pore size distributions for these materials can be tuned by varying the reaction conditions.

Experimental.

The polymerization reactions were carried out in stainless steel reactors (either 10 cm³ or 40 cm³) equipped with sapphire view windows, as described previously.¹⁸ The polymers were removed from the reactor as dry, white, continuous monoliths. (SAFETY NOTE: These reactions form porous materials which fill almost the entire volume of the reaction vessel. To minimize any risk that residual CO₂ could be trapped within the polymer matrix, the system was typically allowed to stand overnight after venting *before* opening the reactor.) For porosity / surface area analysis, the monoliths were crushed and sieved to a particle size of greater than 2 mm, in order to eliminate any contribution from fine powder. Porosity and surface area were measured by a combination of mercury intrusion porosimetry and nitrogen adsorption / desorption (BET method).¹⁸

Results and Discussion.

Figure 1 shows a series of electron micrographs for a fractured polymer monolith, synthesised using scCO₂ as the porogen. The material was formed by the free-radical polymerization of trimethylolpropane trimethacrylate (TRM) (see caption for reaction conditions). The polymer is highly porous, as can be seen in the lower micrograph. Initially, a clear, homogeneous solution of CO₂, TRM and initiator (AIBN) was formed at room temperature. The mixture was then heated to 50°C, whereupon polymerisation was initiated.

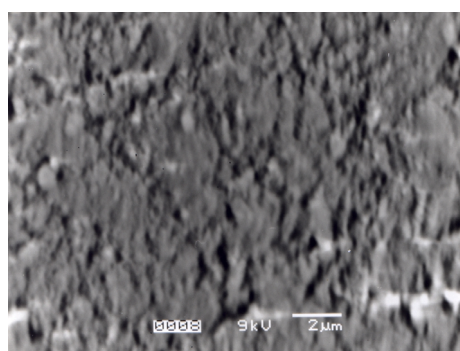
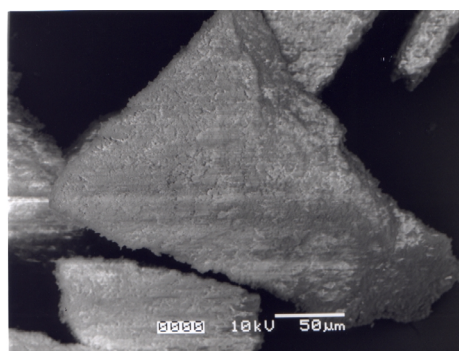
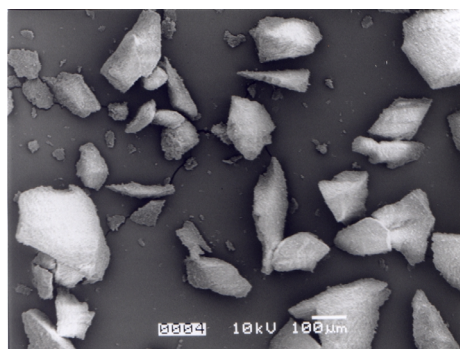


Figure 1. SEM images showing a fractured porous monolith at increasing magnification. Surface area = 328 m²/g. Median pore diameter = 20 nm. (Samples were sputter-coated with 2 nm gold before analysis.) Scale bar = 100 μm (top), 50 μm (middle) and 2 μm (bottom). *Reaction conditions:* TRM (60 % v/v), CO₂ (40 % v/v, 310 bar), AIBN (2 % w/v based on TRM), 50°C, 12 h.

After approximately 20–30 minutes, the solution became translucent (*i.e.*, gelation of the CO₂ / monomer mixture). After 2 hours, the mixture appeared white and opaque, indicating phase separation. The CO₂ was vented and the polymer was removed as a dry, white cylindrical monolith which conformed precisely to the shape of the reactor. The pressure could be vented quite rapidly (over a period of a few minutes) and no cracking of the materials was observed. This process differs from the method described by Beckman^{20,21} in that the TRM-based polymer is much more rigid and highly cross-linked: as a consequence, pore growth *via* gas expansion was not a viable mechanism and the pore structure of these materials was not microcellular (Fig 1), but rather consisted of a series of interconnected channels between fused particles. It was found that the monomer concentration had a very strong influence on the porous properties of monoliths formed *via* this route.¹⁸ For example, the monolith shown in Fig. 1 was prepared from a 60:40 v/v TRM : CO₂ mixture, and had a median pore diameter of 20 nm and a surface area of 328 m²/g. By contrast, a similar monolith prepared from a 40:60 v/v TRM : CO₂ mixture, was found to have a median pore diameter of 7880 nm and a surface area of just 5.2 m²/g.

In general, higher monomer concentrations led to smaller average pore sizes and larger surface areas. Below a threshold monomer concentration of between 30–35 % v/v, monolithic products were *not* formed, and polymers were isolated as free-flowing microgel powders.¹⁷ Variation in monomer concentration led to the formation of materials with average pore sizes and surface areas

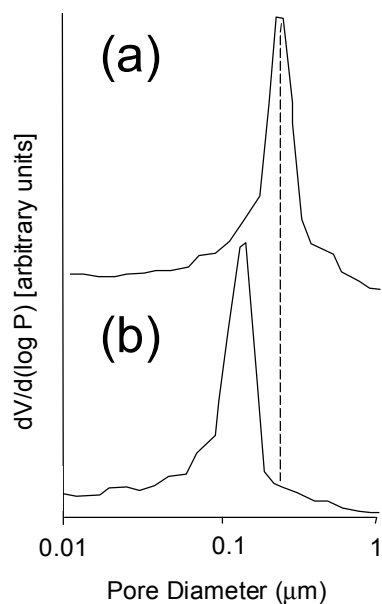


Figure 2. Pore size distributions (as measured by Hg intrusion porosimetry) for polymer monoliths synthesized at two different CO_2 pressures. (a) $P(\text{CO}_2) = 155$ bar; (b) $P(\text{CO}_2) = 310$ bar. Reaction conditions: TRM (50 % v/v), CO_2 (50 % v/v), AIBN (2 % w/v based on TRM), 50°C , 12 h.

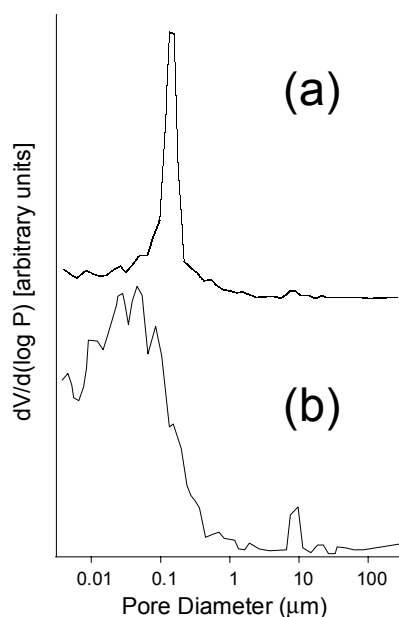


Figure 3. Pore size distributions illustrating the effect of reverse micellar imprinting using scCO_2 as the porogenic solvent. Reaction conditions: (a) TRM (50 % v/v), CO_2 (50 % v/v); (b) TRM (50 % v/v), CO_2 (37.5 % v/v), H_2O (12.5 % v/v), AOT (4 % w/v based on H_2O); (a) + (b) AIBN (2 % w/v based on TRM), 50°C , 12 h.

which spanned a very broad range (*i.e.*, 10 nm–8000 nm, 5–350 m^2/g). One of our aims was to identify methods whereby these properties could be ‘fine tuned’ for particular applications. Firstly, our results indicate that it is possible to influence pore size distributions by varying the CO_2 pressure (and hence the CO_2 density). Figure 2 shows pore size distributions for porous monoliths synthesised at two different pressures [(a) 155 bar; (b) 310 bar]. All other reaction variables were exactly equivalent in the two experiments. It is clear that the monolith synthesised at the higher pressure [Fig. 2(b)] has significantly smaller pores (100 nm vs 185 nm) and a correspondingly larger surface area (269 m^2/g vs 89 m^2/g). This is analogous to varying pore size by changing the porogenic solvent composition, and our early results are in accordance with previous studies where an increase in the porogenic solvent strength led to smaller average pore diameters and larger surface areas.^{19,20}

Another method for the control of pore size distributions in cross-linked polymers is ‘reverse micellar imprinting,’ as described by Zhu *et al.*^{21,22} We have shown that this can be achieved in scCO_2 by polymerizing TRM in the presence of an aqueous microemulsion, which acts as a template for pore formation. When TRM was polymerized at 50 v/v % in scCO_2 , the pore size distribution was narrow and unimodal, peaking at around 100 nm [Figure 3(a)]. When the experiment was repeated in the presence of a water-in- CO_2 microemulsion stabilized by sodium bis(2-ethylhexyl) sulfosuccinate (AOT), the pore size distribution was significantly broader and shifted to include a wide range of pores with much smaller diameters [median pore diameter = 25 nm, Figure 3(b)]. Before polymer phase separation, a clear, transparent aqueous microemulsion was observed in the reaction vessel. Previous studies have shown that it is very difficult to form stable aqueous microemulsions in *pure* scCO_2 by using conventional surfactants, and highly fluorinated stabilizers have usually been required.²³ The stability of the microemulsions in our experiments was presumably a result of the high concentration (40–60 % v/v) of monomer in the CO_2 phase.

Conclusions.

We conclude that it is possible to synthesize well-defined, highly porous cross-linked monoliths using scCO_2 as a non-solvating porogenic diluent. We have demonstrated the synthesis of polymers with narrow, unimodal pore size distributions, without the use of complex ternary solvent mixtures. The separation of solvent from polymer is very simple, and no solvent residues are left in the polymer after depressurization. This may be useful, for example, in the formation of molded macroporous polymers within narrow bore capillaries, where the removal of the porogenic solvent can be difficult. Preliminary results show that it is possible to fine-tune the pore size distribution with pressure or by reverse micellar imprinting. We believe that our methods may be applied to the synthesis of a wide range of porous materials, and that the approach may be particularly valuable for the preparation of specialized cross-linked porous materials for applications that involve subsequent re-exposure to supercritical fluid solvents.

Acknowledgements.

We gratefully acknowledge the EPSRC, the Ramsay Memorial Trust, and the Royal Society (University Research Fellowship to AIC) for funding.

Literature Cited.

- (1) Sherrington, D. C. Preparation, structure and morphology of polymer supports. *Chem. Commun.* **1998**, 2275-2286.
- (2) Arshady, R. Suspension, emulsion, and dispersion polymerization - a methodological survey. *Colloid Polym. Sci.* **1992**, 270, 717-732.
- (3) Vivaldo-Lima, E.; Wood, P. E.; Hamielec, A. E.; Penlidis, A. An updated review on suspension polymerization. *Ind. Eng. Chem. Res.* **1997**, 36, 939-969.
- (4) Svec, F.; Fréchet, J. M. J. Continuous rods of macroporous polymer as high-performance liquid chromatography separation media. *Anal. Chem.* **1992**, 64, 820-822.
- (5) Peters, E. C.; Svec, F.; Fréchet, J. M. J. Rigid macroporous polymer monoliths. *Adv. Mater.* **1999**, 11, 1169-1181.
- (6) Cooper, A. I. Polymer synthesis and processing using supercritical carbon dioxide. *J. Mater. Chem.* **2000**, 10, 207-234.
- (7) Kendall, J. L.; Canelas, D. A.; Young, J. L.; DeSimone, J. M. Polymerizations in supercritical carbon dioxide. *Chem. Rev.* **1999**, 99, 543-563.
- (8) DeSimone, J. M.; Guan, Z.; Elsbernd, C. S. Synthesis of fluoropolymers in supercritical carbon dioxide. *Science* **1992**, 257, 945-947.
- (9) DeSimone, J. M.; Maury, E. E.; Menciloglu, Y. Z.; McClain, J. B.; Romack, T. J.; Combes, J. R. Dispersion polymerizations in supercritical carbon dioxide. *Science* **1994**, 265, 356-359.

- (10) Yates, M. Z.; Li, G.; Shim, J. J.; Maniar, S.; Johnston, K. P.; Lim, K. T.; Webber, S. Ambidextrous surfactants for water-dispersible polymer powders from dispersion polymerization in supercritical CO₂. *Macromolecules* **1999**, *32*, 1108-1026.
- (11) Mang, S. A.; Cooper, A. I.; Colclough, M. E.; Chauhan, N.; Holmes, A. B. Copolymerization of CO₂ and 1,2-cyclohexene oxide using a CO₂-soluble chromium porphyrin catalyst. *Macromolecules* **2000**, *33*, 303-308.
- (12) Parks, K. L.; Beckman, E. J. Generation of microcellular polyurethane foams via polymerization in carbon dioxide. 1. Phase behavior of polyurethane precursors. *Polym. Eng. Sci.* **1996**, *36*, 2417-2431.
- (13) Parks, K. L.; Beckman, E. J. Generation of microcellular polyurethane foams via polymerization in carbon dioxide. 2. Foam formation and characterization. *Polym. Eng. Sci.* **1996**, *36*, 2404-2416.
- (14) Shi, C.; Huang, Z.; Kilic, S.; Xu, J.; Enick, R. M.; Beckman, E. J.; Carr, A. J.; Melendez, R. E.; Hamilton, A. D. The gelation of CO₂: a sustainable route to the creation of microcellular materials. *Science* **1999**, *286*, 1540-1543.
- (15) Loy, D. A.; Russick, E. M.; Yamanaka, S. A.; Baugher, B. M.; Shea, K. J. Direct formation of aerogels by sol-gel polymerizations of alkoxysilanes in supercritical carbon dioxide. *Chem. Mater.* **1997**, *9*, 2264-2268.
- (16) Cooper, A. I.; Hems, W. P.; Holmes, A. B. Synthesis of cross-linked polymer microspheres in supercritical carbon dioxide. *Macromol. Rapid Commun.* **1998**, *19*, 353-357.
- (17) Cooper, A. I.; Hems, W. P.; Holmes, A. B. Synthesis of highly cross-linked polymers in supercritical CO₂ by heterogeneous polymerization. *Macromolecules* **1999**, *32*, 2156-2166.
- (18) Cooper, A. I.; Holmes, A. B. Synthesis of molded monolithic porous polymers using supercritical carbon dioxide as the porogenic solvent. *Adv. Mater.* **1999**, *11*, 2170-2175.
- (19) Viklund, C.; Svec, F.; Fréchet, J. M. J.; Irgum, K. Monolithic, “molded”, porous materials with high flow characteristics for separations, catalysis, or solid-phase chemistry: control of porous properties during polymerization. *Chem. Mater.* **1996**, *8*, 744-750.
- (20) Viklund, C.; Pontén, E.; Glad, B.; Irgum, K.; Hörstedt, P. “Molded” macroporous poly(glycidylmethacrylate-co-trimethylolpropane trimethacrylate) materials with fine controlled porous properties: preparation of monoliths using photoinitiated polymerization. *Chem. Mater.* **1997**, *9*, 463-471.
- (21) Zhu, X. X.; Banana, K.; Yen, R. Pore size control in cross-linked polymer resins by reverse micellar imprinting. *Macromolecules* **1997**, *30*, 3031-3035.
- (22) Zhu, X. X.; Banana, K.; Liu, H. Y.; Krause, M.; Yang, M. Cross-linked porous polymer resins with reverse micellar imprints: factors affecting the porosity of the polymers. *Macromolecules* **1999**, *32*, 277-281.
- (23) Johnston, K. P.; Harrison, K. L.; Clarke, M. J.; Howdle, S. M.; Heitz, M. P.; Bright, F. V.; Carlier, C.; Randolph, T. W. Water-in-carbon dioxide microemulsions: an environment for hydrophiles including proteins. *Science* **1996**, *271*, 624-626.